

Manufacture of Canola-Based Polyols for Commercial Polymers

Flora Elvistia Firdaus

Department of Chemical Engineering, Jayabaya University
Jl.Pulomas Selatan Kav 23, Jakarta Timur- 13210, Indonesia
flora_elvistia@yahoo.com

Muhammad Dachyar

Department of Industrial Engineering, Universitas Indonesia
Kampus UI Depok – 16424, Indonesia
mdachyar@yahoo.com

Abstract

Issues related to terms bio-based, biodegradable, and sustainable products has agitated environmental alert from the destructive effects of petrochemicals and their derivatives. The use of occurring molecules from natural resources for the production of industrial polymers and polymeric intermediates has risen attention of academicians and industrial communities. The laboratory work has been scrutinized in years on synthesizing polymers from natural resources. Polyols have brought on markets to manufacture polymer products one of which was polyurethane. The Canola based-polyol was the product modification of triglyceride's natural resource for the polymers production prepared for wide applications. This study was aimed to determine the optimize of manufacturing canola based epoxide and canola based polyol.

Keywords

Canola based polyols, vegetable oils, natural resources, triglyceride

1. Introduction

Edible oils became the most attainable chemicals for manufacturing green products which in contrast to the depletable petroleum oil. The polyols from the natural resource for the preparation of polymer chemicals are priceless compared to petroleum-based polyester and the existing market are rapidly expanded. Manufacturing polymers from vegetable oils triglycerides along with their different types of fatty acids attributes are linked to a glycerol molecule through ester groups. The reaction were initially introduce the hydroxyl (-OH) groups into carbon-carbon double bonds in the vegetable oils to be chemically reacted to peroxy acids. The reaction proceeds through an epoxidation step then resulted in an unstable oxirane ring by acids to finally obtain polyols which contained hydroxyl groups (Hu et al., 2002). The transformation was involved in a manufacture synthetic pathway, where the reactions were not very selective as can be indicated from the by-products obtained. Applying conventional methods to producing polyols will not result in a significant hydroxyl group with desirable viscosity to be proceeded to urethanes or others polymers' products (F.E. Firdaus, 2016). There are still some doubt toward the existence of a completely renewable-based polyol, where the OH groups formation from unsaturated triglyceride (Garrison, Kessler, & Larock, 2014), are expected to be more reactive to isocyanates for instance to forming polyurethane. However, the utilization of renewables for polyol has reactivated interest to minimize the dependency on petrochemicals that are now in shortage. Several methods were employed to functionalize the less reactive, low molecular weight for the competitive bio-based polyols (Lubguban et al., 2017).

The requirement of polyols for bio-polymers product must supported by the proper methods for the high unsaturated double carbon bonds of vegetable oils. The existing methods has resulted hydroxyl number of commercial polyol an oxirane ring opening by alcohols with hydroxyl number 270–310 mgKOH/g of the soybean oil which limit the applicability as flexible polyurethane foam. The largest non-functional branches in saturated fatty acid have caused to reducing reactivity which in general will affect the final foam properties (Petrović, Zhang, & Javni, 2005). Polyurethanes (PURs) foams were acquired through the reaction of polyols and isocyanates(Tanaka, Hirose, & Hatakeyama, 2008); (Calvo-Correas, Mosiewicki, Corcuera, Eceiza, & Aranguren, 2015), where the commercial of

both are predominantly from petroleum. However, there are trends to materials usage based on renewable resources (Zhou, Sain, & Oksman, 2016), such as starch, sugar, and lignin (Abdel Hakim, Nassar, Emam, & Sultan, 2011); (D'Souza, Camargo, & Yan, 2014); (F.E. Firdaus, 2011a), where often the polyols from synthetics are in part or entirely compensated by bio polyols.

Bio-based polyols from various vegetable oils such as palm (Pawlik & Prociak, 2012), soy (Campanella, Bonnaillie, & Wool, 2009), linseed (Calvo-Correas et al., 2015), rapeseed (Pawlik & Prociak, 2012); tung (Mosiewicki, Casado, Marcovich, & Aranguren, 2008); (Soto, Marcovich, & Mosiewicki, 2016), and castor oil (Mosiewicki, Dell'Arciprete, Aranguren, & Marcovich, 2009). It can be achieved by an establishment of hydroxyl groups into the double bonds or ester bonds. The epoxides products followed by the opening ring of oxiranes by an active hydrogen atoms through several reaction; hydroformylation, ozonolysis and hydrogenation, transesterification, and transamidation. The contrasting approach of modifying natural oils to bio-polyols has made the research on bio-polyols rich of references.

The structure of polyols has cogent influence on the final properties of PUR foams, which also depends on the foaming process (Arbenz, Frache, Cuttica, & Avérous, 2016); (F.E. Firdaus, 2011b). The addition of bio-polyols can be prepared for flexible and rigid PURs synthesis which changed both physical and chemical properties of PUR foams and resulted in a more systemized cellular structure (Pawlik & Prociak, 2012); (Prociak, Rojek, & Pawlik, 2012). Bio-polyols for flexible foams synthesis are usually have hydroxyl number in the range of 50–200 mg KOH/g (Campanella et al., 2009); (Prociak et al., 2012); (C. Zhang, Madbouly, & Kessler, 2015); (F.E. Firdaus, 2014), with higher apparent density. The foams with the inclusion of 15% of bio-polyol had almost twice the tensile strength, which are three times greater compressive stress at 40% strain compared petrochemical foams. The increasing of bio-polyols can affected to the increasing of foams' resilience (Prociak et al., 2012) (Pawlik & Prociak, 2012), more smaller cell sizes in the cellular images, and the foams mechanical properties as well as the apparent density. Bio-polyols of the rigid PURs foam synthesis usually required more highly hydroxyl numbers in the range of 250-400 mg KOH/g (Kosmela, Hejna, Formela, Haponiuk, & Piszczyk, 2018). The rapeseed oil derivatives are possibly replaced petroleum-based PURs up to 80 wt% the products are beneficial for heat insulation, it indicated through the closed-cell structures. Using glycerol according to several references are proven as chain extender, crosslinkers which also performed as plasticizer during the polyurethane synthesis (Flora Elvístia Firdaus & Firdaus, 2014).

This study aimed to determine the optimize of manufacturing of canola-based epoxide and canola-based polyol from variables of concentration of acid catalyst, temperatures, and time of reactions. Identify the functional groups which governed the polyols molecular by the support of FTIR and NMR ¹H and ¹²C. Forecasting the proceed products of the existing property.

2. Materials and Method

The canola oil was purchased from the local grocery store. Hydrogen peroxide (35%), sodium sulfate anhydrous, glycerol technical grade were retrieved from Harum Kimia Indonesia. Sulfuric acid 96% was obtained from Mekar Jati, Indonesia. NaHCO₃ and Na₂SO₄ from Harum Kimia Indonesia. The diphenyl methylene diisocyanate (pMDI was manufacture by Bayer Corporation, Germany), where the NCO contentment was 31.5 wt% with functionality 2.6 as administered from supplier.

2.1.Synthesis of Canola Based Epoxide

The epoxidation reaction in unsaturated triglycerides is an initial reaction that must be passed before the next reaction forms polyols. In the epoxidation reaction carried out on canola oil, the ratio of CH₃COOH and H₂O₂ was calculated by stoichiometry (F.E. Firdaus, 2010). The reaction will proceed well using an sulfuric acid catalyst where the concentration variables are 1%; 1.3%; 1.5%; 1.6%; 1.7%; 1.9%; and 2% (v/v) it was done *in situ* with the volume of previous canola oil was 100 mL and the time of reaction was 100 minutes, then determined the oxirane number (mg KOH/g) of canola based epoxide.

The oxirane number was determined through milliliters of sodium hydroxide. A 2 gram sample was poured into 250 mL Erlenmeyer flask dissolved in neutralized 96% ethyl alcohol. Heat it if necessary, cooled to room temperature. Titrate with phenolphthalein end point with 0.1N sodium hydroxide solution (Swern, Findley, Billen, & Scanlan, 1947).

2.2.Synthesis of Canola Based Polyol

The resulted canola epoxidized were added to a stirred with the mixture of epoxide to 1,2 diethylene glycol (glycerol) with the ratio 1:5 (mol/mol) than added concentrated sulfuric acid of 1.5 (% w/w) to investigate the hydroxyl number of polyols. The reaction was stirred continuously at 60°C and 70°C for 90;100; and 120 minutes (Kong, Liu, & Curtis, 2012). Then optimized the formula. Certainly, a balance volume of ethyl acetate was added, the solution washed with water then the organic layer was washed with NaHCO₃ and brine, dried with anhydrous Na₂SO₄, filtered, and finally concentrated using an evaporator. Determined the hydroxyl number and acid number.

2.3.Determination The Hydroxyl number and Acid Number of Polyol

The acid number of polyol are usually used to ensure batch-to-batch uniformity, using correction

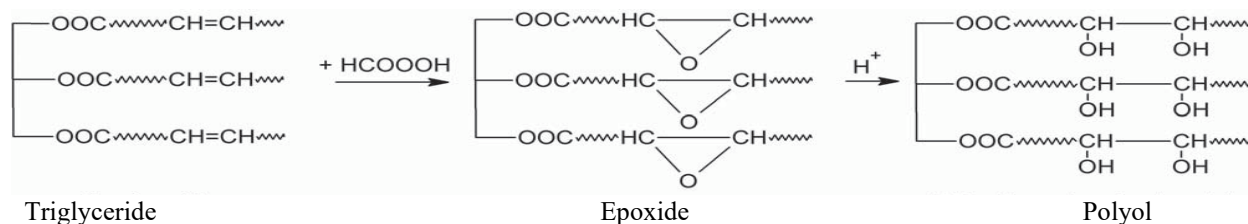


Figure 1. Scheme Manufacturing The Synthetic Pathway of Polyols from natural Canola Oil (Calvo-Correas et al., 2015)

factor for the true hydroxyl number. They were determined according to ASTM D4662. The multiple hydroxyl groups of polyols correlates to the amount of polyols according to ASTM E1899. The general scheme of the polyol synthesis depicted in Figure 1.

3. Result and Discussion

Characterization of Epoxide

For the ratio of CH₃COOH and H₂O₂ 1/3.66 (mol/mol), the best concentration of sulfuric was 1.5% by weight with a temperature 60°C in 100 minutes. This conditions has resulted the highest oxirane number, was 5.8 mg KOH/g, as can be seen in Table 1.

Table 1. The effect ratio of CH₃COOH/H₂O₂ (1/3.66)(mol/mol) to The Production of Canola Based Epoxide

CH ₃ COOH/H ₂ O ₂ (mol/mol)	% vol Catalyst	Temp. (deg C)	Time (Minute)	Oxirane (mg KOH/g)
1/3.66	1%	60	90	4.5
1/3.66	1%	60	100	5
1/3.66	1.50%	60	100	5.8
1/3.66	1.70%	60	100	5.4 5.3
1/3.66	2%	60	100	Initial solidification
1/3.66	3%	60	100	60% gel

If the acid concentration increased to 2% it initiates the solidification of epoxide product, as well as if the acid was increased up to 3% resulted the gel formation approximately 60% of the yield. If sulfur concentration below the best 1.5% , which was 1% and 1.3%, the oxirane number were not significantly different.

Table 2. The Effect Ratio of $\text{CH}_3\text{COOH}/\text{H}_2\text{O}_2$ (1/3.74)(mol/mol) to The Production of Canola Based Epoxide

$\text{CH}_3\text{COOH}/\text{H}_2\text{O}_2$ (mol/mol)	% vol Catalyst	Temp. (deg C)	Time (Minute)	Oxirane (mg KOH/g)
1/3.74	1.30%	60	100	5.7 5.8
1/3.74	1.50%	60	100	5.6 5.7
1/3.74	1.70%	60	100	4.5 4.5

The reaction time plays an important role for producing highest oxirane number, where 100 minutes produces high epoxide oxirane number than less 100 minutes for 100 mL of canola oil. Increasing the catalyst to 2% has forming an initial solidification of the epoxide, and this was becoming more worsen because the 60% gelling formation. The characterization were done by the support of FTIR and NMR by ^1H and ^{12}C . If the ratio of CH_3COOH with H_2O_2 was increased to 1/3.74 (mol/mol) it was found that the concentration of sulfuric 1.3% (v/v) was not significantly different from 1.5% (v/v), where the number was around 5.7 mg KOH/g at the best temperature of 60°C illustrated in Table 2.

Table 3. The Effect ratio $\text{CH}_3\text{COOH}/\text{H}_2\text{O}_2$ (1/3.89)(mol/mol) to the Production of Canola based Epoxide

$\text{CH}_3\text{COOH}/\text{H}_2\text{O}_2$ (mol/mol)	% vol Catalyst	Temp. (deg C)	Time (Minute)	Oxirane (mg KOH/g)
1/3.89	1.60%	60	100	5.3 5.3
1/3.89	1.70%	60	100	5.6 5.6
1/3.89	1.90%	60	100	5.5

The acid number with the concentration of catalyst 1% was 2.4 and it was 1.1 with the catalyst 1.5%. If the ratio continues to be increased to 1/3.89 and 1/3.97, the best sulfuric concentration was when the oxirane value was the highest. It was found that the best acid catalyst concentration was 1.5% (v/v). At a ratio of 1/3.89, it was tried to increase the acid concentration to the level above 1.5% (v/v), the oxirane number was still in the range of 5.3-5.6 mg KOH/g. Another thing will be found if the temperature was increased to 70°C though the concentration was 1.5% the oxirane tends to decline. Moreover the time extended 10 minutes from 100 minutes there were tends to continues declining, it was most probably the ketones formation. As can be summarized the optimum reaction condition was 60°C, the catalyst was 1.5 (%v/v), and the reaction duration was 120 minutes. It was shown in Table 3 and Figure 2.

The acid number of 1.5% catalyst concentration was 0.4 and was 1.1 with catalyst 2% for the ratio $\text{CH}_3\text{COOH}/\text{H}_2\text{O}_2$ (1:3.97) (mol/mol). Consequently, for commercial point of view utilization the natural-based polyols specifically canola based were commonly mixed with synthetic fossil-based polyols to attain an adequate foam properties. The reason was found, the primary alcohol in the polyols were usually three times more reactive to isocyanates than secondary alcohols (L. Zhang, Jeon, Malsam, Herrington, & Macosko, 2007), this can lead to by-product formation and become problems for the waste disposal and marketable materials (Petrovic, 2008).

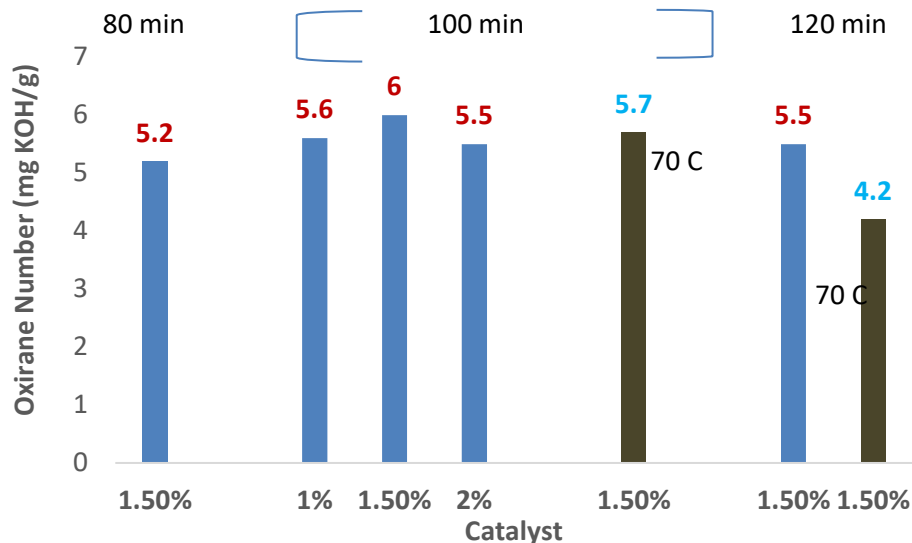


Figure 2. The Optimum Production of Canola Based Polyol at ratio of $\text{CH}_3\text{COOH}/\text{H}_2\text{O}_2$ (1/3.97)(mol/mol) at 60°C . The reaction was done in 80;100; and 120 minutes.

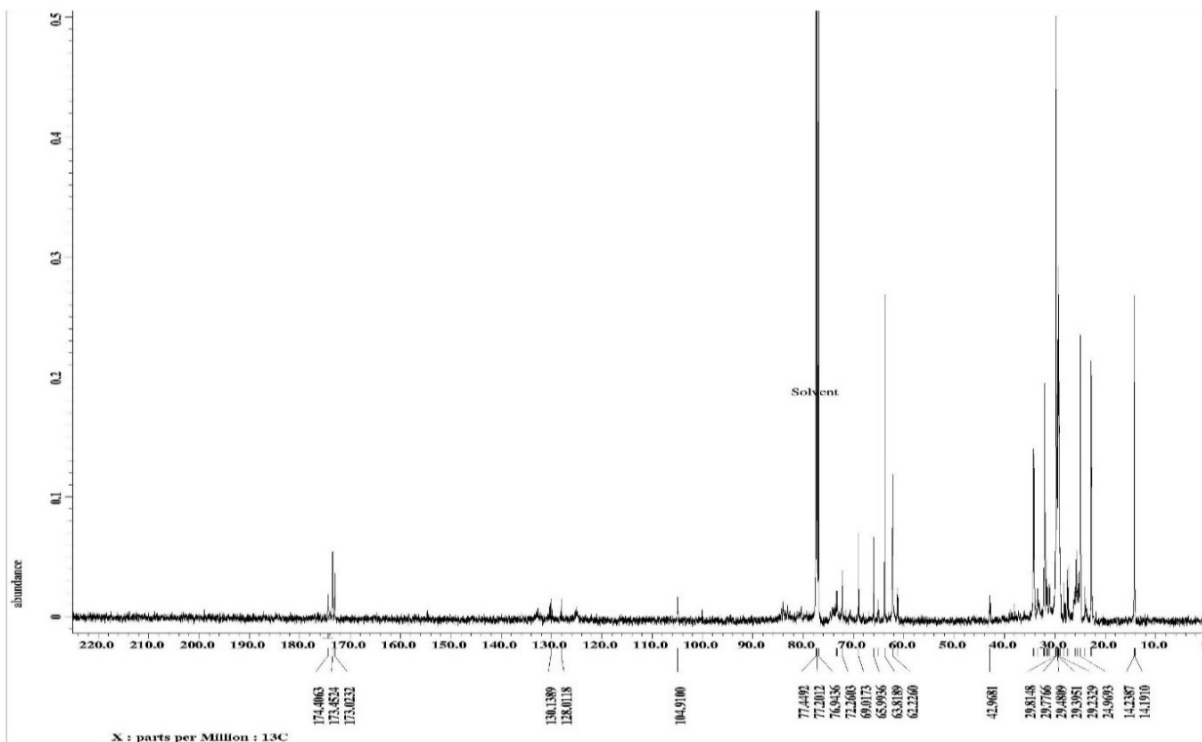


Figure 3. The ^{12}C -NMR of Polyol

The images of The ^{12}C -NMR spectrum of Polyol can be seen in Figure 3 and The ^1H -NMR of Polyol in Figure 4. The FTIR spectrum of the $\text{C}=\text{C}$ bonds of the canola oil have been reduced. The absorption band centered at $3,300\text{ cm}^{-1}$ this was the characteristic of hydroxyl group, which has dissappeared in the saturated triglyceride, but appears in

the other three samples with a tendency to grow in tremendously and extensively. The magnifying scale ^1H -NMR spectrum is depicted in Figure 5.

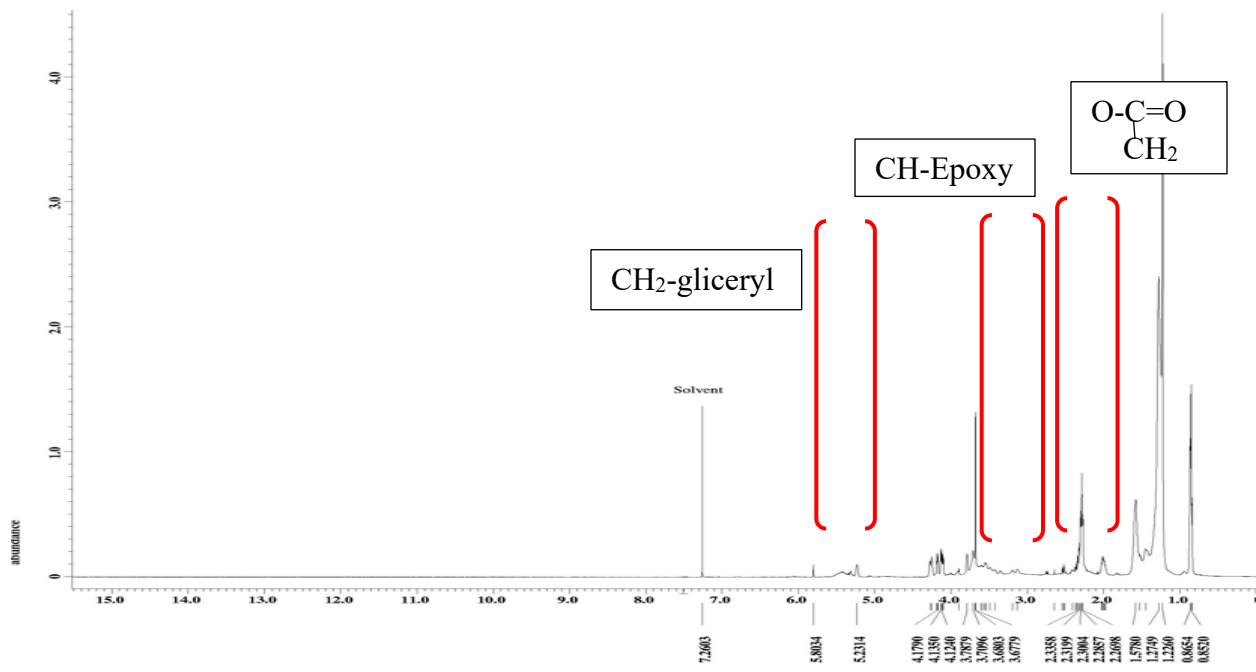


Figure 4. The ^1H -NMR of Polyol

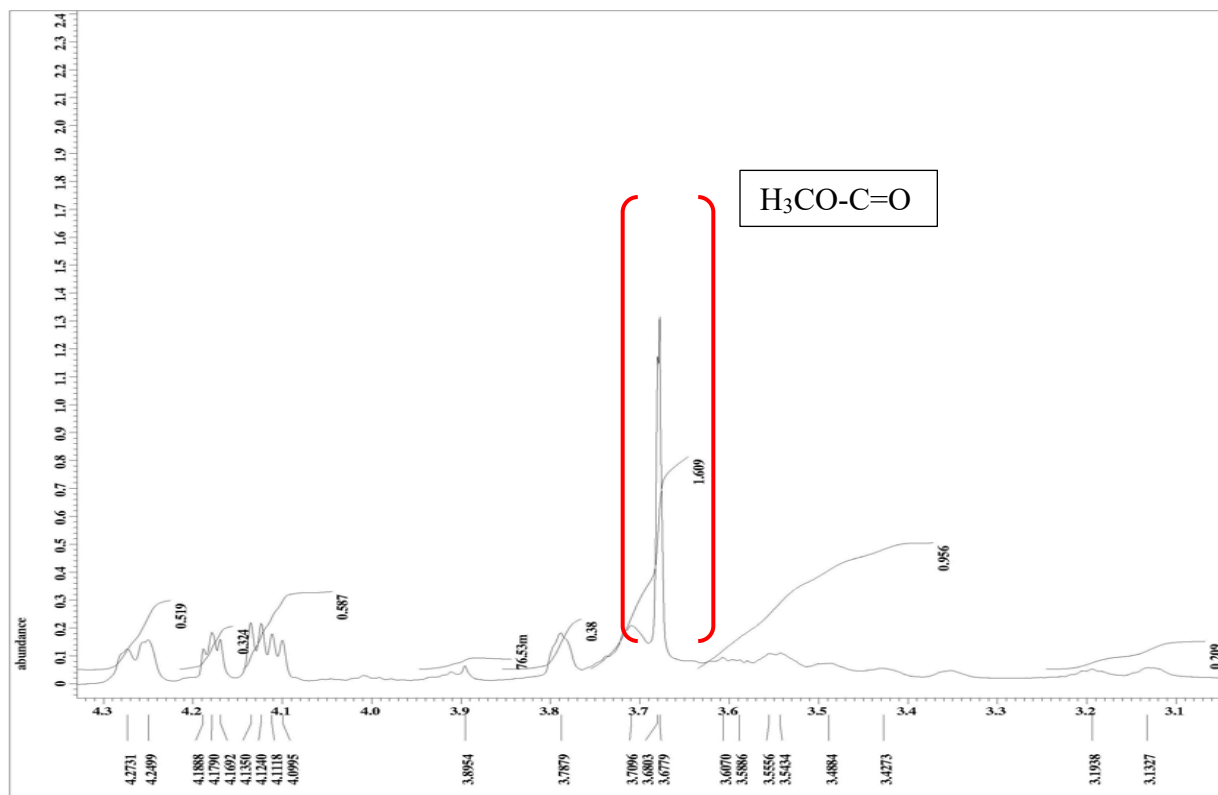


Figure 5. ^1H -NMR in Magnifying scale

The interpretation of the spectrum above as was

$^1\text{H-NMR}$ (Chloroform D 400 MHz): δ 5.23 (m, 1H, CHO- COR), 4.29 (dd, $J = 3.7$ Hz, 2.3 Hz, 2H, CH_2OCOR), 4.179 (dd, $J = 6.0$, 12 Hz, 2H, CH_2OCOR), 3.78 (t, $J = 6.5$ Hz, 4H, CH_2OH), 3.67 (t, $J = 7.5$ Hz, 6H, CH_2CO), 2.268 (m, 10H, $\text{CH}_2\text{CH}_2\text{CO}$ and $\text{CH}_2\text{CH}_2\text{OH}$), 1.27 (m, 44H, CH_2), 0.865 (t, $J = 6.5$ Hz, 3H, CH_3). $^{13}\text{C-NMR}$ (Chloroform D 100 MHz): δ 174.4 (COR, sn-1, 3), 173.45 (COR, sn-1, 3), 170.1 (COR, sn-2), 69.01 (CHOCOR), 63.81 (CH_2OCOR), 62.22 (CH_2OH), 29.81, 29.77, 29.48, 29.39, 29.23, 24.96, 14.23 (CH_3). CI- MS: m/z 693.6 ([M+Na] $^+$).

The optimized hydroxyl value of polyol was in the range 152.4 ± 0.3 to 176.4 ± 0.5 mg KOH/g and the acid value was in the range 22.9 ± 0.1 mg KOH/g (Narine, Yue, & Kong, 2007). The hydroxyl value also given information about degree of esterification. Acid value of polyol shows the presence of OH (hydroxyl) and grouping the type of foam (soft or rigid) from polyol if reacted to isocyanate. The high acid value will produces rigid vice versa.

Conclusion

In this study, the canola oil was employed for the production of polyol prepared for the commercial polymers. From the test results on polyols supported by data from FTIR, NMR ^1H and ^{12}C and the references the position of OH on the Carbon primer was more reactive to isocyanate which leading to the formation of by-products or in other words produces wastes. In terms of production costs, this will not be profitable so it was necessary to add petroleum oil to suppress this reactiveness.

References

- Abdel Hakim, A. A., Nassar, M., Emam, A., & Sultan, M. (2011). Preparation and characterization of rigid polyurethane foam prepared from sugar-cane bagasse polyol. *Materials Chemistry and Physics*, *129*(1–2), 301–307. <https://doi.org/10.1016/j.matchemphys.2011.04.008>
- Arbenz, A., Frache, A., Cuttica, F., & Avérous, L. (2016). Advanced biobased and rigid foams, based on urethane-modified isocyanurate from oxypropylated gambier tannin polyol. *Polymer Degradation and Stability*, *132*, 62–68. <https://doi.org/10.1016/j.polyimdegradstab.2016.03.035>
- Calvo-Correas, T., Mosiewicki, M. A., Corcuera, M. A., Eceiza, A., & Aranguren, M. I. (2015). Linseed oil-based polyurethane rigid foams: Synthesis and characterization. *Journal of Renewable Materials*, *3*(1), 3–13. <https://doi.org/10.7569/JRM.2014.634132>
- Campanella, A., Bonnaillie, L. M., & Wool, R. P. (2009). Polyurethane foams from soyoil-based polyols. *Journal of Applied Polymer Science*. <https://doi.org/10.1002/app.29898>
- D'Souza, J., Camargo, R., & Yan, N. (2014). Polyurethane foams made from liquefied bark-based polyols. *Journal of Applied Polymer Science*, *131*(16), 1–10. <https://doi.org/10.1002/app.40599>
- Firdaus, F.E. (2010). Silicone on blending vegetal petrochemical based polyurethane. *World Academy of Science, Engineering and Technology*, *65*.
- Firdaus, F.E. (2011a). Optimization of soy epoxide hydroxylation to properties of prepolymer polyurethane. *World Academy of Science, Engineering and Technology*, *81*.
- Firdaus, F.E. (2011b). Relationship of reaction temperature on phosphate oligomers reactivity to properties of soy-polyurethane. *World Academy of Science, Engineering and Technology*, *76*.
- Firdaus, F.E. (2014). The selection reaction of homogeneous catalyst in soy-epoxide hydroxylation. *Journal of Physics: Conference Series*, *495*(1). <https://doi.org/10.1088/1742-6596/495/1/012013>
- Firdaus, F.E. (2016). An environmental friendly material: Epoxide-based resin from vegetables oil for bio-fiber reinforced composites. *International Journal of Applied Engineering Research*, *11*(7).
- Firdaus, Flora Elvistia, & Firdaus, F. E. (2014). *Synthesis and Characterization of Soy-Based Polyurethane Foam with Utilization of Ethylene Glycol in Polyol Synthesis and Characterization of Soy-Based Polyurethane Foam with Utilization of Ethylene Glycol in Polyol*. *18*(1), 10–16. <https://doi.org/10.7454/mst.v18i1.2937>
- Garrison, T. F., Kessler, M. R., & Larock, R. C. (2014). Effects of unsaturation and different ring-opening methods on the properties of vegetable oil-based polyurethane coatings. *Polymer*, *55*(4), 1004–1011. <https://doi.org/10.1016/j.polymer.2014.01.014>
- Hu, Y. H., Gao, Y., De Wang, N., Hu, C. P., Zu, S., Vanoverloop, L., & Randall, D. (2002). Rigid polyurethane foam prepared from a rape seed oil based polyol. *Journal of Applied Polymer Science*, *84*(3), 591–597. <https://doi.org/10.1002/app.10311>
- Kong, X., Liu, G., & Curtis, J. M. (2012). Novel polyurethane produced from canola oil based poly(ether ester)

- polyols: Synthesis, characterization and properties. *European Polymer Journal*, 48(12), 2097–2106. <https://doi.org/10.1016/j.eurpolymj.2012.08.012>
- Kosmela, P., Hejna, A., Formela, K., Haponiuk, J., & Piszczyk, Ł. (2018). The Study on Application of Biopolyols Obtained by Cellulose Biomass Liquefaction Performed with Crude Glycerol for the Synthesis of Rigid Polyurethane Foams. *Journal of Polymers and the Environment*, 26(6), 2546–2554. <https://doi.org/10.1007/s10924-017-1145-8>
- Lubguban, A. A., Ruda, R. J. G., Aquiatan, R. H., Paclijan, S., Magadan, K. O., Balangao, J. K. B., ... Suppes, G. J. (2017). Soy-Based Polyols and Polyurethanes. *Kimika*, 28(1), 1–19. <https://doi.org/10.26534/kimika.v28i1.1-19>
- Mosiewicki, M. A., Casado, U., Marcovich, N. E., & Aranguren, M. I. (2008). Vegetable oil based-polymers reinforced with wood flour. *Molecular Crystals and Liquid Crystals*, 484(November 2014), 143/[509]-150/[516]. <https://doi.org/10.1080/15421400801904344>
- Mosiewicki, M. A., Dell'Arciprete, G. A., Aranguren, M. I., & Marcovich, N. E. (2009). Polyurethane foams obtained from castor oil-based polyol and filled with wood flour. *Journal of Composite Materials*, 43(25), 3057–3072. <https://doi.org/10.1177/0021998309345342>
- Narine, S. S., Yue, J., & Kong, X. (2007). Production of polyols from canola oil and their chemical identification and physical properties. *JAOCs, Journal of the American Oil Chemists' Society*, 84(2), 173–179. <https://doi.org/10.1007/s11746-006-1021-5>
- Pawlik, H., & Prociak, A. (2012). Influence of Palm Oil-Based Polyol on the Properties of Flexible Polyurethane Foams. *Journal of Polymers and the Environment*, 20(2), 438–445. <https://doi.org/10.1007/s10924-011-0393-2>
- Petrovic, Z. S. (2008). Polyurethanes from vegetable oils. *Polymer Reviews*, 48(1), 109–155. <https://doi.org/10.1080/15583720701834224>
- Petrović, Z. S., Zhang, W., & Javni, I. (2005). Structure and properties of polyurethanes prepared from triglyceride polyols by ozonolysis. *Biomacromolecules*, 6(2), 713–719. <https://doi.org/10.1021/bm049451s>
- Prociak, A., Rojek, P., & Pawlik, H. (2012). Flexible polyurethane foams modified with natural oil based polyols. *Journal of Cellular Plastics*, 48(6), 489–499. <https://doi.org/10.1177/0021955X12446210>
- Soto, G. D., Marcovich, N. E., & Mosiewicki, M. A. (2016). Flexible polyurethane foams modified with biobased polyols: Synthesis and physical-chemical characterization. *Journal of Applied Polymer Science*, 133(35), 1–11. <https://doi.org/10.1002/app.43833>
- Swern, D., Findley, T. W., Billen, G. N., & Scanlan, J. T. (1947). Determination of Oxirane Oxygen. *Analytical Chemistry*, 19(6), 414–415. <https://doi.org/10.1021/ac60006a018>
- Tanaka, R., Hirose, S., & Hatakeyama, H. (2008). Preparation and characterization of polyurethane foams using a palm oil-based polyol. *Bioresource Technology*, 99(9), 3810–3816. <https://doi.org/10.1016/j.biortech.2007.07.007>
- Zhang, C., Madbouly, S. A., & Kessler, M. R. (2015). Biobased polyurethanes prepared from different vegetable oils. *ACS Applied Materials and Interfaces*, 7(2), 1226–1233. <https://doi.org/10.1021/am5071333>
- Zhang, L., Jeon, H. K., Malsam, J., Herrington, R., & Macosko, C. W. (2007). Substituting soybean oil-based polyol into polyurethane flexible foams. *Polymer*. <https://doi.org/10.1016/j.polymer.2007.09.016>
- Zhou, X., Sain, M. M., & Oksman, K. (2016). Semi-rigid biopolyurethane foams based on palm-oil polyol and reinforced with cellulose nanocrystals. *Composites Part A: Applied Science and Manufacturing*, 83, 56–62. <https://doi.org/10.1016/j.compositesa.2015.06.008>

Biographies

Flora Elvistia Firdaus, is an Associate Professor at the Department of Chemical Engineering at Jayabaya University Jakarta, Indonesia. Research interest; polymer production, environmental engineering, and material composite.

Muhammad Dachyar, is a Professor in Industrial Engineering at Universitas Indonesia, Depok Indonesia. Research Interest; Operation Management and Project Management.